

Tunneling spectra of submicron $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ intrinsic Josephson junctions: Evolution from superconducting gap to pseudogap

S. P. Zhao, X. B. Zhu, and H. Tang

*Beijing National Laboratory for Condensed Matter Physics,
Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China*

Tunneling spectra of near optimally doped, submicron $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ intrinsic Josephson junctions are presented, and examined in the region where the superconducting gap evolves into pseudogap. The spectra are analyzed using a self-energy model, proposed by Norman *et al.*, in which both quasiparticle scattering rate Γ and pair decay rate Γ_Δ are considered. The density of states derived from the model has the familiar Dynes' form with a simple replacement of Γ by $\gamma_+ = (\Gamma + \Gamma_\Delta)/2$. The γ_+ parameter obtained from fitting the experimental spectra shows a roughly linear temperature dependence, which puts a strong constraint on the relation between Γ and Γ_Δ . We discuss and compare the Fermi arc behavior in the pseudogap phase from the tunneling and angle-resolved photoemission spectroscopy experiments. Our results indicate an excellent agreement between the two experiments, which is in favor of the precursor pairing view of the pseudogap.

PACS numbers: 74.50.+r, 74.25.Jb, 74.72.Hs

I. INTRODUCTION

Pseudogap in cuprate superconductors is now a well established phenomenon,¹ but its nature remains a mystery. There are theories that provide viable candidates for the origin of the pseudogap. Some of them involve precursor superconductivity,^{2,3} such as those based on boson-mediated pairing⁴ or bipolaron^{5,6} scenario, or on the resonating valence bond state.⁷ Other theories like the nearly antiferromagnetic Fermi liquid model⁸ have also been proposed. Moreover, pseudogap can arise from a different origin such as charge density wave that competes with the superconducting state.⁹ Apparently, understanding pseudogap is crucial for finding the underlying pairing mechanism of the cuprate superconductors.

One important observation in the pseudogap phase from angle-resolved photoemission spectroscopy (ARPES) experiments is the existence of an ungapped portion on the Fermi surface, described through the spectral function $A(\mathbf{k}, \omega)$, known as the Fermi arc.¹⁰ Recently, there has been considerable progress towards its understanding. ARPES measurements on $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ (Bi-2212) materials demonstrated a linear temperature dependence of arc length above T_c ¹¹ and the opening of a gap on the arc below T_c .^{12,13} Further analysis of the ARPES,^{14,15} Raman, and specific heat data¹⁶ showed that the arc is interpretable from a linear temperature dependence of the quasiparticle scattering rate Γ .

Tunneling has traditionally been a useful tool in revealing the material's superconducting properties.^{17,18} For the Bi-2212 materials, experimental techniques including scanning tunneling microscope (STM),¹⁹ break junctions (BJs),²⁰ and intrinsic Josephson junctions (IJJs)^{21,22,23,24,25,26} were used, yielding a variety of valuable results. For instance, Zasadzinski *et al.* analyzed the BJ and STM data using the d -wave Eliashberg theory and correlated the tunneling dip feature with the

magnetic resonance mode.²⁰ These studies point to the electron coupling to a narrow boson spectrum as possible pairing mechanism. From the STM results,¹⁹ the pseudogap opening temperature T^* , rather than T_c , was suggested to be the mean-field critical temperature, thus supporting precursor pairing as the origin of the pseudogap phase. Meanwhile, in the IJJ studies, a different observation, namely the coexistence of the superconducting gap and pseudogap, which leads to the conclusion that their origins are different, was reported.^{21,22,23} Viewing from these results, it is clear that the answer to the pseudogap nature is still ambiguous from the tunneling experiments using different techniques. Further understanding is therefore needed, in particular on the above-mentioned Fermi arc issue that has not been addressed so far in the reported tunneling experiments.

In this paper, we present and examine the tunneling spectra of near optimally doped, submicron Bi-2212 IJJs near and above T_c where the superconducting gap evolves into pseudogap.²⁷ We show that the spectra can be well fitted using the density of states (DOS) in a form often used in the tunneling experiment:²⁸

$$N(\theta, \omega) = \text{Re} \left[\frac{\omega + i\gamma_+}{\sqrt{(\omega + i\gamma_+)^2 - \Delta^2 \cos^2(2\theta)}} \right], \quad (1)$$

where a d -wave gap is considered and θ is the angle of in-plane momentum measured from $(\pi, 0)$. Such fit leads to a slowly decreasing Δ and a roughly linear behavior of γ_+ with increasing temperature. It can be easily shown that Eq. (1) is closely related to the phenomenological self-energy:³

$$\Sigma(\mathbf{k}, \omega) = -i\Gamma + \frac{\Delta_{\mathbf{k}}^2}{\omega + \epsilon_{\mathbf{k}} + i\Gamma_\Delta}, \quad (2)$$

where $\epsilon_{\mathbf{k}}$ is the energy of bare electrons relative to the value at the Fermi surface and Γ_Δ comes from the pair fluctuations. The self-energy in Eq. (2), applicable for

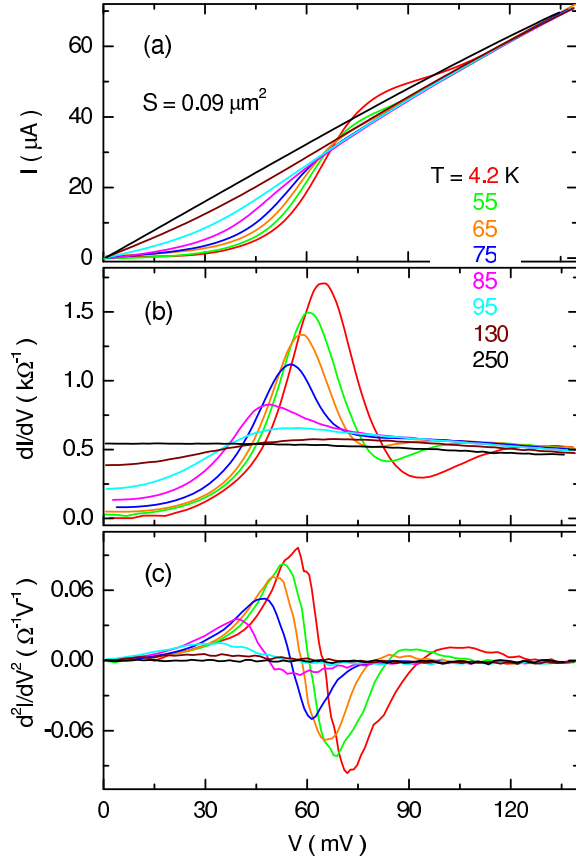


FIG. 1: (Color online) (a) I - V , (b) dI/dV , and (c) d^2I/dV^2 characteristics of a near optimally doped, submicron Bi-2212 mesa ($T_c = 89$ K) containing 10 IJJs. V corresponds to the voltage per IJJ.

the description of precursor superconductivity, was used recently to discuss the Fermi arcs from ARPES experiment assuming $\Gamma = \Gamma_\Delta$.^{14,15} In the present work, we will consider the more general case where $\Gamma \neq \Gamma_\Delta$ based on the experimentally obtained tunneling parameters, and compare the data with the ARPES experiment. As will be seen below, our results demonstrate a remarkable consistency between the two experiments, which is in favor of the precursor pairing view of the pseudogap.

II. TUNNELING SPECTRA OF SUBMICRON IJJS NEAR OPTIMAL DOPING

IJJs, being intrinsic, have the advantage of avoiding the problems like the surface deterioration and unstable junction structure, and can offer a convenient temperature or magnetic-field dependent measurement. When the IJJ size decreases, the sample's self-heating, a main obstacle in the IJJ studies, will also decrease.²⁹ Recently, we showed that self-heating can be reduced significantly when junction sizes decrease down to the submicron level.^{24,25} In Fig. 1, we plot the tunneling spectra of an IJJ mesa, $0.3 \mu\text{m}$ in size, fabricated on a Bi-2212

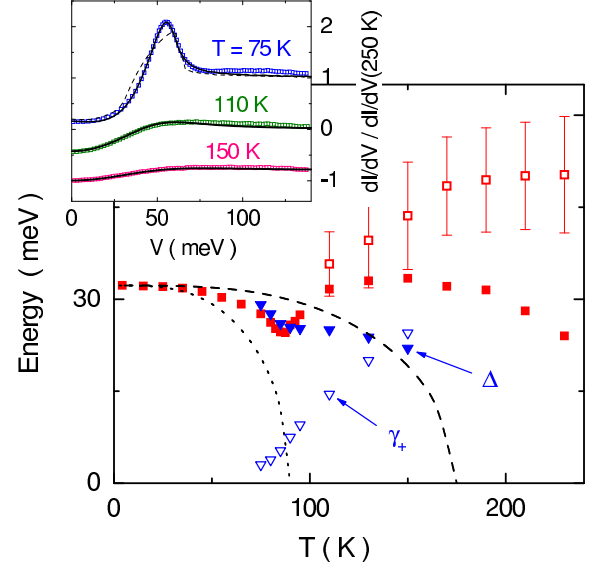


FIG. 2: (Color online) Half the dI/dV peak energy Δ_p (solid squares). Open squares are those from the spectra normalized to the one at 250 K. Solid and open triangles are Δ and γ_+ in Eq. (1) from fitting the spectra using $N_{eff}(\omega)$. The dashed and dotted lines are the BCS d -wave $\Delta_p(T)$ with $2\Delta_p(0)/kT_c = 4.28$ and that with temperature normalized to T_c , respectively. The inset shows the normalized spectra at three temperatures (symbols), and the calculated results using N_{eff} (solid lines) and $N_d(\omega)$ (dashed line at 75 K). The 110 and 150 K curves are shifted downwards for clarity.

crystal with $T_c = 89$ K. The spectra show a well-defined normal-state resistance $R_N \sim 1.92 \text{ k}\Omega$, and clear low- T dip feature³⁰ as observed in the BJ experiment.²⁰ It is seen that as temperature increases, the superconducting peak shifts to lower voltages and its strength weakens. Near T_c , the superconducting gap smoothly evolves into pseudogap that persists up to temperatures as high as 230 K, similar to the STM results.¹⁹ In Fig. 2, we plot half the dI/dV peak energy Δ_p as solid squares, while the open squares represent the corresponding data for the spectra normalized to the one at 250 K. Both data show a slope change near 150 K, which is reminiscent of the experiments suggesting two pseudogap temperatures T_1^* and T_2^* (230 and 150 K, respectively, in the present case), such as Nernst experiment.^{7,31}

In Fig. 1, the dI/dV dip disappears at ~ 70 K, which allows simple I - V curve calculations¹⁸ to fit the data near and above T_c using a θ -averaged DOS:²⁰

$$N_d(\omega) = (1/2\pi) \int_0^{2\pi} N(\theta, \omega) d\theta, \quad (3)$$

or an effective DOS:

$$N_{eff}(\omega) = (1/\pi) \int_0^{2\pi} N(\theta, \omega) \cos^2(2\theta) d\theta, \quad (4)$$

in which tunneling with a directional preference is considered.^{26,32} In Eqs. (3) and (4), $N(\theta, \omega)$ is given by Eq. (1), which has the Dynes' form²⁸ and is used frequently in fitting the experimental tunneling spectra for both BCS¹⁸ and cuprate^{20,32} superconductors. In the inset of Fig. 2, we show the normalized experimental spectra at three temperatures (symbols) together with the calculated results (lines). From the data at 75 K, it can be seen that the result using $N_{eff}(\omega)$ (solid line) fits the experimental spectrum much better than that using $N_d(\omega)$ (dashed line). The fitting parameters Δ and γ_+ using $N_{eff}(\omega)$ are plotted in Fig. 2 as solid and open triangles, respectively. The results show that Δ has a weak temperature dependence while γ_+ increases roughly linearly with temperature. At about $T_2^* = 150$ K, γ_+ becomes larger than Δ .

III. BASIC FORMULAS

Eq. (1) can be derived from the self-energy in Eq. (2) under certain appropriate approximations, which can therefore be used as a starting point to compare the tunneling and ARPES experiments. First of all, we note that Fermi arcs in the ARPES experiment are usually discussed through the spectral function $A(\mathbf{k}, \omega)$ on the Fermi surface. It is considered to be gapped if $A(k_F, \omega)$ has maxima at $\omega = \pm\omega_p \neq 0$ (we call it ARPES gap below for convenience), while Fermi arc appears at places where $A(k_F, \omega)$ has maximum only at $\omega = 0$. From the self-energy in Eq. (2), it can be easily shown that the Green's function $G(\mathbf{k}, \omega) = 1/[\omega - \epsilon_{\mathbf{k}} - \Sigma(\mathbf{k}, \omega)]$ has the form

$$G(\mathbf{k}, \omega) = \frac{\omega + i\Gamma_{\Delta} + \epsilon_{\mathbf{k}}}{(\omega + i\Gamma - \epsilon_{\mathbf{k}})(\omega + i\Gamma_{\Delta} + \epsilon_{\mathbf{k}}) - \Delta_{\mathbf{k}}^2}, \quad (5)$$

therefore $A(k_F, \omega) = -(1/\pi)\text{Im}G(k_F, \omega)$, assuming $\Delta_{\mathbf{k}} = \Delta \cos(2\theta)$, is given by

$$A(\theta, \omega) = \frac{1}{\pi} \frac{\Gamma_{\Delta}[\Delta^2 \cos^2(2\theta) + \Gamma\Gamma_{\Delta}] + \Gamma\omega^2}{[\omega^2 - \Delta^2 \cos^2(2\theta) - \Gamma\Gamma_{\Delta}]^2 + \omega^2(\Gamma + \Gamma_{\Delta})^2}. \quad (6)$$

In a special case of $\Gamma = \Gamma_{\Delta}$, the above equation becomes

$$A(\theta, \omega) = \frac{\Gamma}{\pi} \frac{\omega^2 + \Delta^2 \cos^2(2\theta) + \Gamma^2}{[\omega^2 - \Delta^2 \cos^2(2\theta) - \Gamma^2]^2 + 4\omega^2\Gamma^2}, \quad (7)$$

which was used by Norman *et al.*¹⁴ and Chubukov *et al.*¹⁵ to interpret Fermi arcs in terms of the Γ parameter. Tunneling experiments, on the other hand, are discussed through DOS, which is defined by $-(1/\pi) \sum_{\mathbf{k}} \text{Im}G(\mathbf{k}, \omega)$.

In Eliashberg's strong-coupling theory of BCS superconductors, the summation over $\mathbf{k}$ is safely replaced by an integration $\int_{-\infty}^{\infty} d\epsilon_{\mathbf{k}}$ and the strong-coupling DOS with a

complex gap function $\Delta(\omega)$ can be obtained.¹⁷ In the present case for the Bi-2212 materials, we can follow the same procedure if we assume a circular Fermi surface¹⁵ and $\Delta_{\mathbf{k}} = \Delta \cos(2\theta)$. This is possible since, considering a tight-binding dispersion like $\alpha + 2\beta(\cos k_x + \cos k_y)$ where α and β are constants, the DOS in the *normal* state has a slow variation with energy for all θ . A simple derivation, with the introduction of

$$\gamma_{\pm} = \frac{\Gamma \pm \Gamma_{\Delta}}{2}, \quad (8)$$

shows that Eq. (2) directly leads to Eq. (1). In the case of $\Gamma = \Gamma_{\Delta}$, it becomes

$$N(\theta, \omega) = \text{Re} \left[\frac{\omega + i\Gamma}{\sqrt{(\omega + i\Gamma)^2 - \Delta^2 \cos^2(2\theta)}} \right], \quad (9)$$

which is the familiar Dynes' DOS phenomenologically proposed over three decades ago.²⁸

IV. VISUALIZING FERMİ ARCS USING THE TUNNELING PARAMETERS

The γ_+ parameter in Fig. 2, obtained from fitting the experimental spectra and defined by Eq. (8), provides a strong constraint on the relation between Γ and Γ_{Δ} . The Γ_{Δ} parameter, representing the Cooper pair decay rate, has been discussed previously for the BCS^{34,35} and cuprate³ superconductors. In the case of BCS superconductors, it was taken into account to explain the fluctuation effect above T_c in materials such as aluminum, where a DOS proposed by de Gennes for gapless superconductivity has been used.³⁴ From a general consideration, Γ_{Δ} should be zero below T_c and is known to have a linear temperature dependence above it:^{34,35}

$$\Gamma_{\Delta} = \begin{cases} 0, & \text{for } T < T_c, \\ \frac{8}{\pi} k_B (T - T_c), & \text{for } T \geq T_c. \end{cases} \quad (10)$$

The Γ_{Δ} behavior was also discussed in the case of cuprate superconductors. In fitting the ARPES data of underdoped Bi-2212 material with $T_c \sim 83$ K, the linear temperature dependence of Γ_{Δ} was confirmed, but the values were twice as large as the BCS weak-coupling case predicted in Eq. (10).

For known Γ_{Δ} , the Γ parameter can be found from Eq. (8) with experimentally determined γ_+ values in Fig. 2, and the spectral function $A(\theta, \omega)$ can be calculated from Eq. (6). The dashed lines with open symbols in Fig. 3 are such evaluated Γ_{Δ} and Γ parameters using Eq. (10). The Γ parameter thus obtained shows an enhanced and clear nonlinearity in its temperature dependence, while γ_+ exhibits only a small nonlinearity. In Fig. 4(a), we show the calculated results of $A(\theta, \omega)$ using the Δ , Γ , and Γ_{Δ} data at $T = 150$ K for 10 different

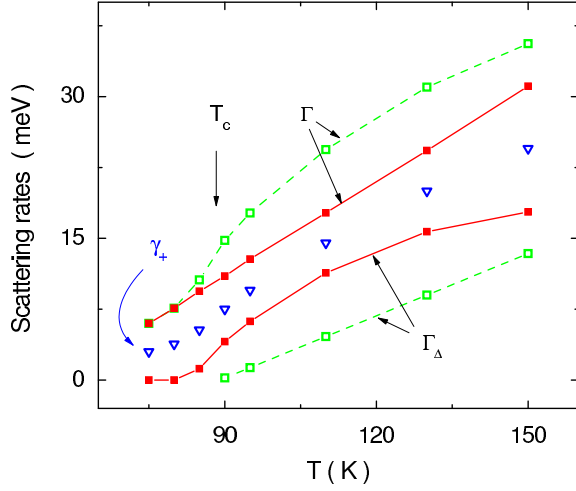


FIG. 3: (Color online) Two sets of the scattering rates Γ and Γ_{Δ} obtained from experimentally determined γ_+ parameter using Eq. (8), assuming Γ_{Δ} in Eq. (10) (dashed lines with open symbols), and a Γ linearly increasing with temperature starting from below T_c (solid lines with full symbols).

θ values ranging from 0 to 45° . For small θ (antinode region), the curves show two peaks at $\pm\omega_p$ symmetric to $\omega = 0$. As θ increases, the two peaks shift to smaller $|\omega|$ and between $\theta = 35^\circ$ and 40° , they merge into a single peak at $\omega = 0$, thus forming the Fermi arc as discussed in the ARPES experiment. Fig. 4(b) shows the corresponding DOS from Eq. (1), in which the gapped structure disappears only at the nodal point of $\theta = 45^\circ$.

The ARPES gap ω_p can be found by setting the first derivative of Eq. (6) to zero:

$$\omega_p^2 = (1 + \frac{\Gamma_{\Delta}}{\Gamma})\Delta \cos(2\theta)\sqrt{\eta} - \frac{\Gamma_{\Delta}}{\Gamma}\eta, \quad (11)$$

where $\eta = \Delta^2 \cos^2(2\theta) + \Gamma\Gamma_{\Delta}$. By setting the second derivative to zero, the angle θ_0 at which the arc starts is found to be

$$\theta_0 = 0.5 \cos^{-1}(\sqrt{\frac{\Gamma_{\Delta}}{\Gamma + 2\Gamma_{\Delta}}} \frac{\Gamma_{\Delta}}{\Delta}). \quad (12)$$

Fig. 5 displays ω_p as a function of θ at two typical temperatures $T = 75$ and 150 K (solid lines). At $T = 75$ K $< T_c$, we have $\Gamma_{\Delta} = 0$ and from Eq. (11), ω_p equals the full d -wave gap $\Delta \cos(2\theta)$. At $T = 150$ K, one can clearly see the existence of the Fermi arc above $\theta_0 \sim 37^\circ$. The dotted line is the d -wave gap $\Delta \cos(2\theta)$ at the same temperature plotted for comparison. In Fig. 5, we also show the result at $T = 150$ K under the special condition $\Gamma = \Gamma_{\Delta} = \gamma_+$ (dashed line). The corresponding $A(\theta, \omega)$ is displayed in the inset of Fig. 4, which shows $\theta_0 \sim 25^\circ$. Setting $\Gamma = \Gamma_{\Delta}$ at 150 K leads to the Γ_{Δ} value approximately twice as large as that given by Eq. (10), as can be seen in Fig. 3. In this case, both ARPES gap and Fermi arc show considerable differences. In Fig. 6,

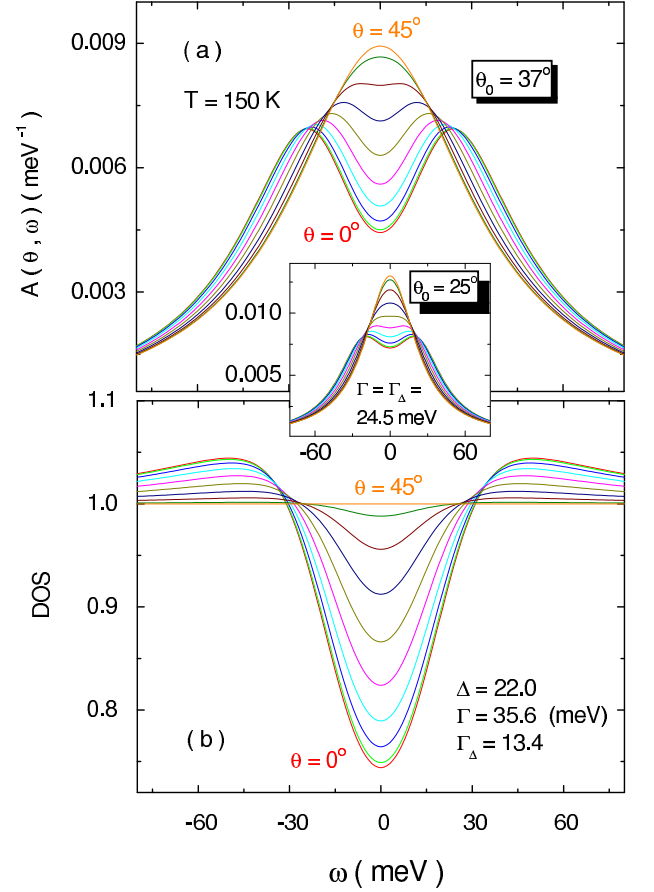


FIG. 4: (Color online) Spectral function $A(\theta, \omega)$ on the Fermi surface at 150 K calculated from Eq. (6) using Δ , Γ , and Γ_{Δ} parameters indicated. Curves are plotted with θ step of 5° . (b) Corresponding results of DOS from Eq. (1). The Γ and Γ_{Δ} parameters are taken from the dashed lines with open symbols at 150 K in Fig. 3. The inset shows $A(\theta, \omega)$ with equal Γ and Γ_{Δ} at the same temperature.

the relative arc length l_{arc} , defined by

$$l_{arc} = 1 - (\frac{4}{\pi})\theta_0, \quad (13)$$

is calculated from the Γ and Γ_{Δ} parameters of dashed lines with open symbols in Fig. 3, and is plotted as open symbols. The dashed line in the figure is a guide to the eye, which extends to about 45 percent of the full Fermi surface length near T_1^* .

V. DISCUSSION

Using Bi-2212 samples at various doping levels, Kanigel *et al.*¹¹ found the arc length above T_c varying as T/T^* , extrapolating to zero as $T \rightarrow 0$, and rapidly increasing from about 50 percent to the full Fermi surface length near T^* . This result is explained using the self-energy model Eq. (2) in the case of $\Gamma = \Gamma_{\Delta}$ and assuming a constant Δ and a linear $\Gamma \propto T$ at all T .¹⁴

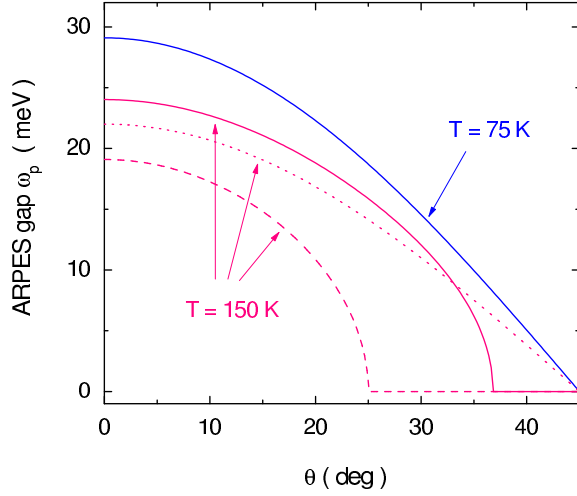


FIG. 5: (Color online) ARPES gap ω_p versus θ at $T = 75$ and 150 K calculated from Eq. (11) with Γ and Γ_Δ taken from the dashed lines with open symbols in Fig. 3 (solid lines). The dashed line is the result at $T = 150$ K with equal $\Gamma = \Gamma_\Delta = 24.5$ meV. The dotted line is the d -wave gap $\Delta \cos(2\theta)$ at $T = 150$ K shown for comparison.

In the present case with single doping sample, if we use Eq. (10) to define Γ_Δ , we see that the arc length above T_c has approximately a linear temperature dependence and approaches about 45 percent of the full Fermi surface length near T_1^* , but it extrapolates to zero as $T \rightarrow T_c$, as is shown by the dashed line with open symbols in Fig. 6. Such temperature dependence of the arc length is similar to the discussion in Ref. 15 where the actual $\Gamma \sim T$ dependence from the ARPES measurements³³ is taken. However, it deviates from the experimental observations as reported in Refs. 11 and 13.

In the present case of $\Gamma \neq \Gamma_\Delta$ we are considering, we find that there exist alternative choices of the Γ and Γ_Δ parameters that can lead to a better explanation. Instead of setting the Γ_Δ parameter first from Eq. (10), we can start in a reverse way by assuming a Γ linearly increasing with temperature, which extends from the data below T_c where $\Gamma_\Delta \rightarrow 0$. Such a linear temperature-dependent quasiparticle scattering rate was predicted in the marginal Fermi-liquid theory for the cuprate superconductors³⁶ and has been discussed in a number of experiments. The Γ parameter from this consideration is shown in Fig. 3 as a solid line with full symbols, together with the Γ_Δ parameter obtained from the experimentally determined γ_+ through Eq. (8). We can see that the Γ_Δ parameter thus obtained exhibits a faster rise with increasing temperature near T_c . The relative arc length l_{arc} calculated from Eq. (13) using this set of parameters is plotted in Fig. 6 as full symbols, which shows a clear difference compared to that with open symbols. From the solid line in the figure, one can see that the arc length would extrapolate to zero as $T \rightarrow 0$, which is in an excellent agreement with the ARPES experiment.^{11,13}

Experimentally, an ARPES gap opening on the

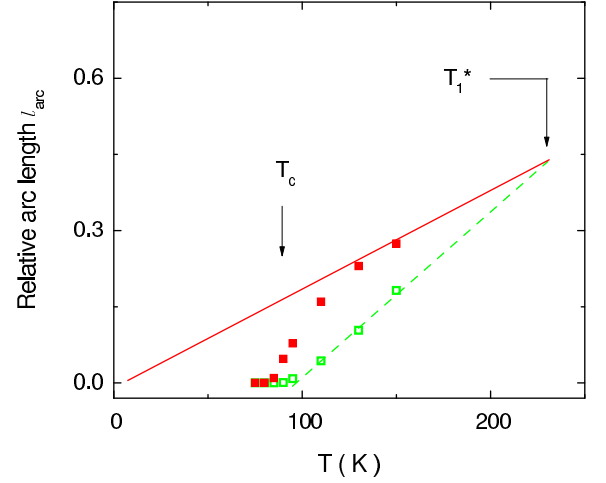


FIG. 6: (Color online) Relative arc length l_{arc} calculated from Eq. (13) using Δ in Fig. 2 and Γ and Γ_Δ in Fig. 3. Open and solid symbols correspond to the Γ and Γ_Δ parameters shown as dashed line with open symbols and solid line with full symbols in Fig. 3, respectively. Two straight lines are guides to the eye.

Fermi arc as temperature decreases right below T_c was observed.^{12,13} The gap opening can be gradual and follow the BCS-like temperature dependence¹² or has a sudden increase to the full d -wave gap size.¹³ Our results, based on the tunneling data and the self-energy model in Eq. (2), seem to support the latter observation provided Γ_Δ is zero or vanishingly small below T_c as is shown in Fig. 3. Above T_c , the Fermi arc exists and the θ -dependence of the ARPES gap significantly deviates from the d -wave gap behavior. One interesting feature from our calculated results in Fig. 5 is that the ARPES gap for smaller θ at 150 K (solid line) surpasses that of the d -wave gap (dotted line). Such a tendency may be compared to a recent ARPES measurement on the $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$ material,³⁷ where a clear evidence was found that near the antinodal region the ARPES gap is enhanced and has a larger gap size compared to the d -wave gap behavior near the nodal region. Possible origins of the antinodal phenomenology including a gap opening with strong quasiparticle scattering were mentioned in Ref. 37.

The above discussion reveals a consistent picture from the key ARPES observations and the corresponding results obtained from the tunneling experiment through the phenomenological self-energy in Eq. (2). The consistency appears remarkable considering that only θ - and energy-independent parameters Γ and Γ_Δ are employed, and the only assumption used is a linear temperature-dependent quasiparticle scattering rate Γ , which should be reasonable for the cuprate superconductors.

It is worth emphasizing that the ARPES gap, from the description of Eq. (2), needs not always to be the energy gap $\Delta \cos(2\theta)$. It can be zero (forming the Fermi arc) or larger than $\Delta \cos(2\theta)$ depending on the values of Γ and

Γ_Δ . On the other hand, the gap parameter Δ from fitting the experimental spectra in Fig. 2 (solid triangles) shows a distinct behavior compared to the BCS temperature dependence (dashed and dotted lines). It decreases quickly as T approaches from below T_c and there is a sudden slope change at T_c . It sits slightly higher than that obtained directly from the dI/dV peak position (solid squares in the figure) below T_c . Above T_c , their separation increases. In Fig. 2, one can also see that Δ tends to be finite up to $T_1^* = 230$ K, which in the precursor pairing view suggests T_1^* to be the mean-field critical temperature as discussed in the STM experiment.¹⁹

The strange Δ behavior near T_c could be caused by the loss of the global coherence of Cooper pairs where the Δ parameter should be understood as the thermodynamic-averaged value $\langle \Delta^2 \rangle$.^{34,35} In any case, the differences between half the dI/dV peak position, Δ , and the system's "true" superconducting gap parameter can be expected. At temperatures above T_c , for example, the dI/dV peak position becomes largely affected by the increasing Γ and Γ_Δ (see Fig. 2), as in the case of the BCS superconductors.³⁴ Also, our d -wave Eliashberg analysis²⁶ considering a bosonic spectrum^{20,26} has resulted in a satisfactory fit for the 4.2 K curves in Fig. 1 and a low- T gap parameter $\Delta_0 \sim 38$ meV as defined from the gap function $\Delta(\omega)$ by $\Delta_0 = \Delta(\Delta_0)$.¹⁷ This Δ_0 value, corresponding to the peak position of the antinodal DOS from the theory, is greater than that obtained from the dI/dV peak position (~ 32 meV, see Fig. 2), which gives rise to $2\Delta_0/kT_1^* \sim 3.83$ close to the BCS d -wave ratio of 4.28.

VI. CONCLUSION

Tunneling spectra of near optimally doped, submicron $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ intrinsic Josephson junctions were presented, and examined in the region near and above T_c where the superconducting gap evolves into pseudogap. We showed that the spectra can be well fitted using the density of states in the familiar Dynes' form, which is closely related to a self-energy model proposed recently to discuss the Fermi arc phenomena observed in the ARPES experiment. In this work, we considered a general situation where the quasiparticle scattering rate Γ and pair decay rate Γ_Δ in the model are independent parameters, related however through $\gamma_+ = (\Gamma + \Gamma_\Delta)/2$. We compared the Fermi arc behavior in the pseudogap phase from the tunneling and ARPES experiments, and showed that from the experimentally determined γ_+ parameter, some key ARPES results can be derived based upon only one assumption: a linear temperature-dependent Γ . This demonstrates a remarkable consistency between the two experiments, which is in favor of the precursor pairing view of the pseudogap.

We are grateful to L. Y. Zhang, T. Xiang, N. L. Wang, and Q. H. Wang for many valuable discussions. We thank M. R. Norman for pointing out Ref. 3 to us. This work was supported by the Ministry of Science and Technology of China (2006CB601007), the Knowledge Innovation Project of the Chinese Academy of Sciences, and the National Natural Science Foundation of China (10604064).

-
- ¹ T. Timusk and B. Statt, Rep. Prog. Phys. **62**, 61 (1999).
 - ² V. J. Emery and S. A. Kivelson, Nature **374**, 434 (1995); A. Kanigel, U. Chatterjee, M. Randeria, M. R. Norman, G. Koren, K. Kadowaki, and J. C. Campuzano, arXiv:cond-mat/0803.3052v1 (2008).
 - ³ M. R. Norman, M. Randeria, H. Ding, and J. C. Campuzano, Phys. Rev. B **57**, R11093 (1998).
 - ⁴ M. R. Norman and A. V. Chubukov, Phys. Rev. B **73**, R140501 (2006).
 - ⁵ A. S. Alexandrov and A. F. Andreev, arXiv:cond-mat/0005315v3 (2000).
 - ⁶ K. A. Müller, in *Handbook of High-Temperature Superconductivity*, edited by J. R. Schrieffer and J. S. Brooks, (Springer, New York, 2007).
 - ⁷ P. A. Lee, N. Nagaosa, and X.-G. Wen, Rev. Mod. Phys. **78**, 17 (2006).
 - ⁸ D. Pines, Physica C **282-287**, 273 (1997).
 - ⁹ J. X. Li, C. Q. Wu, and D. H. Lee, Phys. Rev. B **74**, R184515 (2006).
 - ¹⁰ M. R. Norman, H. Ding, M. Randeria, J. C. Campuzano, T. Yokoya, T. Takeuchi, T. Takahashi, T. Mochiku, K. Kadowaki, P. Guptasarma, and D. G. Hinks, Nature **392**, 157 (1998).
 - ¹¹ A. Kanigel, M. R. Norman, M. Randeria, U. Chatterjee, S. Souma, A. Kaminski, H. M. Fretwell, S. Rosenkranz, M. Shi, T. Sato, T. Takahashi, Z. Z. Li, H. Raffy, K. Kadowaki, D. Hinks, L. Ozyuzer, and J. C. Campuzano, Nat. Phys. **2**, 447 (2006).
 - ¹² W. S. Lee, I. M. Vishik, K. Tanaka, D. H. Lu, T. Sasagawa, N. Nagaosa, T. P. Devereaux, Z. Hussain, and Z.-X. Shen, Nature **450**, 81 (2007).
 - ¹³ A. Kanigel, U. Chatterjee, M. Randeria, M. R. Norman, S. Souma, M. Shi, Z. Z. Li, H. Raffy, and J. C. Campuzano, Phys. Rev. Lett. **99**, 157001 (2007).
 - ¹⁴ M. R. Norman, A. Kanigel, M. Randeria, U. Chatterjee, and J. C. Campuzano, Phys. Rev. B **76**, 174501 (2007).
 - ¹⁵ A. V. Chubukov, M. R. Norman, A. J. Millis, and E. Abraham, Phys. Rev. B **76**, R180501 (2007).
 - ¹⁶ J. G. Storey, J. L. Tallon, G. V. M. Williams, and J. W. Loram, Phys. Rev. B **76**, R060502 (2007).
 - ¹⁷ J. R. Schrieffer, *Theory of Superconductivity*, (Benjamin, New York, 1964).
 - ¹⁸ E. L. Wolf, *Principles of Electron Tunneling Spectroscopy*, (Oxford University Press, New York, 1985).
 - ¹⁹ C. Renner, B. Revaz, J.-Y. Genoud, K. Kadowaki, and ϕ . Fischer, Phys. Rev. Lett. **80**, 149 (1998); C. Renner, B. Revaz, K. Kadowaki, I. Maggio-Aprile, and ϕ . Fischer, Phys. Rev. Lett. **80**, 3606 (1998); M. Kugler, ϕ . Fischer, C. Renner, S. Ono, and Yoichi Ando, Phys. Rev. Lett. **86**, 4911 (2001).
 - ²⁰ J. F. Zasadzinski, L. Ozyuzer, L. Coffey, K. E. Gray, D. G. Hinks, and C. Kendziora, Phys. Rev. Lett. **96**, 017004

- (2006); J. F. Zasadzinski, L. Ozyuzer, N. Miyakawa, K. E. Gray, D. G. Hinks, and C. Kendziora, *Phys. Rev. Lett.* **87**, 067005 (2001).
- ²¹ V. M. Krasnov, A. Yurgens, D. Winkler, P. Delsing, and T. Claeson, *Phys. Rev. Lett.* **84**, 5860 (2000).
 - ²² M. Suzuki, T. Watanabe, and A. Matsuda, *Phys. Rev. Lett.* **82**, 5361 (1999); M. Suzuki and T. Watanabe, *Phys. Rev. Lett.* **85**, 4787 (2000).
 - ²³ M.-H. Bae, J.-H. Park, J.-H. Choi, H.-J. Lee, and K.-S. Park, *Phys. Rev. B* **77**, 094519 (2008).
 - ²⁴ X. B. Zhu, Y. F. Wei, S. P. Zhao, G. H. Chen, H. F. Yang, A. Z. Jin, and C. Z. Gu, *Phys. Rev. B* **73**, 224501 (2006).
 - ²⁵ X. B. Zhu, S. P. Zhao, Y. F. Wei, H. F. Yang, C. Z. Gu, H. W. Yu, and Y. F. Ren, *Physica C* **460-462**, 963 (2007).
 - ²⁶ S. P. Zhao, X. B. Zhu, and Y. F. Wei, *arXiv:cond-mat/0703177v2* (2007).
 - ²⁷ Part of the data near and *below* T_c is presented in Ref. 25.
 - ²⁸ Eq. (1) is identical in form to the DOS proposed by Dynes *et al.* with a change of sign before γ_+ , which does not affect the DOS value. However, the original Γ parameter is replaced by γ_+ , which is given by Eq. (8) below. See R. C. Dynes, V. Narayanamurti, J. P. Garno, *Phys. Rev. Lett.* **41**, 1509 (1978).
 - ²⁹ V. M. Krasnov, A. Yurgens, D. Winkler, and P. Delsing, *J. Appl. Phys.* **89**, 5578 (2001); V. M. Krasnov, M. Sandberg, and I. Zogaj, *Phys. Rev. Lett.* **94**, 077003 (2005).
 - ³⁰ Clear dip features, resulting from current overshoot above the R_N line near 80 mV, were observed in the submicron IJJs from over 20 crystals fabricated.
 - ³¹ Yayu Wang, Lu Li, M. J. Naughton, G. D. Gu, S. Uchida, and N. P. Ong, *Phys. Rev. Lett.* **95**, 247002 (2005).
 - ³² L. Ozyuzer, J. F. Zasadzinski, C. Kendziora, and K. E. Gray, *Phys. Rev. B* **61**, 3629 (2000).
 - ³³ M. R. Norman, A. Kaminski, J. Mesot, and J. C. Campuzano, *Phys. Rev. B* **63**, R140508 (2001).
 - ³⁴ R. W. Cohen, B. Abeles, and C. R. Fuselier, *Phys. Rev. Lett.* **23**, 377 (1969).
 - ³⁵ M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, New York, 1996).
 - ³⁶ C. M. Varma, P. B. Littlewood, S. Schmitt-Rink, E. Abrahams, and A. E. Ruckenstein, *Phys. Rev. Lett.* **63**, 1996 (1989).
 - ³⁷ R. H. He, K. Tanaka, S. K. Mo, T. Sasagawa, M. Fujuta, T. Adachi, N. Mannella, K. Yamada, Y. Koike, Z. Hussain, and Z.-X. Shen, *Nat. Phys.* **5**, 119 (2009).